



#### AUTHORS:

Olusegun Y. Omogunloye   
Naven Chetty   
Abiola O. Ilori

#### AFFILIATION:

School of Chemistry and Physics,  
University of KwaZulu-Natal,  
Pietermaritzburg, South Africa

#### CORRESPONDENCE TO:

Naven Chetty

#### EMAIL:

chettyn3@ukzn.ac.za

#### DATES:

Received: 02 Sep. 2023

Revised: 16 Oct. 2024

Accepted: 30 Oct. 2024

Published: 27 Mar. 2025

#### HOW TO CITE:

Omogunloye OY, Chetty N, Ilori AO. Radiological risk assessment of cement used in contemporary South African buildings. S Afr J Sci. 2025;121(3/4), Art. #16778. <https://doi.org/10.17159/sajs.2025/16778>

#### ARTICLE INCLUDES:

- ☒ Peer review
- ☐ Supplementary material

#### DATA AVAILABILITY:

- ☐ Open data set
- ☒ All data included
- ☒ On request from author(s)
- ☐ Not available
- ☐ Not applicable

#### EDITORS:

Michael Inggs   
Thywill Dzogbewu

#### KEYWORDS:

activity concentrations, radiological hazards, cement, radionuclides, excess lifetime cancer risk

#### FUNDING:

None



# Radiological risk assessment of cement used in contemporary South African buildings

Using a calibrated NaI(Tl) and a well-shielded detector connected to a computer-resident quantum multichannel analyser, the radionuclide contents of primordial radionuclides ( $^{226}\text{Ra}$ ,  $^{232}\text{Th}$  and  $^{40}\text{K}$ ) were evaluated in commonly used cement brands in South Africa, and the associated radiation risk parameters were calculated. The reported activity concentrations varied from  $8.00 \pm 2.83$  to  $45.00 \pm 2.79$  Bq/kg,  $12.00 \pm 0.90$  to  $32.00 \pm 0.51$  Bq/kg and  $454.00 \pm 0.56$  to  $1765.00 \pm 0.93$  Bq/kg for  $^{226}\text{Ra}$ ,  $^{232}\text{Th}$  and  $^{40}\text{K}$ , respectively. The absorbed gamma dose rate, annual effective dose equivalent, annual gonadal dose equivalent, excess lifetime cancer risk, gamma index and alpha index were utilised as the radiological health impact metrics to evaluate the potential radiation risks. The determined radiological health impact parameter results were below the relevant radiation safety authorities' recommended reference levels for building materials. Therefore, the use of cement products as building materials presents no significant risk in the study areas.

#### Significance:

The results of this study contribute to understanding the radiological risks associated with different brands of commonly used cement in South Africa and provide fundamental data for the activity concentrations of primordial radionuclides  $^{226}\text{Ra}$ ,  $^{232}\text{Th}$  and  $^{40}\text{K}$ . These studies have been instructive from a building materials radiation safety viewpoint and reveal that the assessed risk parameters fall within the recommended safety limits. This is significant from the perspective of environmental health and radiological protection concerning the safe use of the studied cement. The methodology and findings can also inform similar studies in other regions, enhancing global awareness of material safety standards.

## Introduction

It is indeed of great significance to have a better knowledge of the risk associated with the radiation emitted from dwellings due to the various building materials that contain radionuclides of different types, which constitute radiation exposure to the resident.<sup>1</sup> The radiation exposure takes place daily, and the capability of radionuclides to quickly find their way into the air makes them be transferred into human environments.<sup>2,3</sup> Most humans spend approximately 80% of their lifetime indoors, so assessing the radionuclide contents in cement used as building materials and related radiological health hazards for humans is essential.<sup>4</sup> Naturally occurring radionuclides of primordial origin in types of cement used as building materials are responsible for irradiation in dwellings.<sup>5</sup> The radiations come from potassium-40 and gamma radiation from the uranium and thorium families.<sup>6</sup> Gamma radiation exposure causes external exposure when it is directly absorbed.<sup>7</sup> Internal exposure, however, is brought on by radium-226 and thorium-232, as well as their daughter nuclides, including radon-222 and thoron-220, and their progenies.<sup>8</sup> Varying degrees of radiation exposure in man have been reported to lead to deterministic and stochastic effects, including cancer and genetic defects such as chromosome aberrations and mutation.<sup>9,10</sup>

The South African population has increased annually by about 2% since 1980.<sup>11</sup> In the same vein, South Africa's sales of types of cement have progressively increased from 7 million tonnes in 1980 to 11 million tonnes in 2010.<sup>12</sup> There is a clear indication of a corresponding increase in demand for housing as a basic human need due to population increase. Therefore, to cater to the ever-increasing demand for housing by the populace, increased demands for construction materials are inevitable. In both rural and urban areas of South Africa, cement is one of the most essential building materials used to construct homes and other structures.<sup>13</sup> It is used in concrete and block production, flooring and covering of the building floors and walls.<sup>13</sup> Thus, cement has played and will keep on playing significant roles in meeting South Africa's developmental agenda because buildings with cement as an essential component are virtually everywhere.<sup>14</sup> Buildings must contain cement because of its many beneficial properties, such as its 'bond'-like function, its role in filling the spaces between fine and coarse aggregates and its hydration reaction properties that allow buildings to gain strength continuously<sup>15</sup>, and until now, no suitable materials with better or similar qualities have been discovered as an alternative to cement in buildings.

The research on primordial radionuclide concentrations in cement used as building materials in numerous countries throughout the world has garnered much attention over the years.<sup>16-18</sup> The determination of radioactivity concentrations in cement is essential to assess the possible radiological health hazards to residents and to develop radiation protection strategies and reference levels for optimising the protection of the public when using and managing cement as a building material, as required by the International Atomic Energy Agency's (IAEA) General Safety Requirements (GSR) Part 3.<sup>19</sup> The study emphasises the importance of investigating radiation exposure from building materials containing radionuclides to understand and mitigate associated risks, aligning with the IAEA GSR Part 3 frameworks and the International Commission on Radiological Protection (ICRP) Publication 103.<sup>19,20</sup> Therefore, we sought to evaluate the radiological health and safety risks associated with radiation exposure due to the radioactivity concentrations of the primordial radionuclides ( $^{226}\text{Ra}$ ,  $^{232}\text{Th}$  and  $^{40}\text{K}$ ) in cement commonly used for buildings in South Africa.

## Materials and methods

### Collection and preparation of samples

Samples of cement were obtained from multiple suppliers of building materials in Pietermaritzburg, South Africa. The sampling was purposive, focusing on commonly used brands in the area that represent a significant portion of the market. Specifically, cement samples were collected from suppliers stocking products from the Pretoria Portland Cement Company (PPC), Natal Portland Cement Company (NPC) and Dangote Cement South Africa (Sephaku). These brands were selected based on their prevalence and representation in the local construction industry. The sample size was determined based on practical considerations and standard practices in environmental and materials science research.<sup>2,18</sup> The collected samples were air-dried and sieved with a 2-mm mesh for homogeneity. An amount of 200 g of each sample was placed in Marinelli bottles with the same shape as the reference material for gamma spectrometric analysis. The bottles were well-labelled and sealed tightly with tape to prevent radon escape. There were a total of seven samples divided among three popular cement brands.

### Gamma spectrometric analysis

The radioactivity concentrations of the naturally occurring radionuclides in the studied samples were measured with a thallium-doped sodium iodide (NaI(Tl)) gamma-ray spectrometric system at the Radiation Physics Research Laboratory of the University of Medical Sciences, Ondo, Ondo State, Nigeria. A multichannel computer-resident quantum analyser (MCA2100R) and a well-shielded detector were attached to the system. Spectral analysis was done using Palmtop MCA computer gamma analysis software (Model: MCA8k-01, Serial: 0202).

The reference standard source for the detector efficiency calibration was the Analytical Quality Control Service (AQCS, USA), which validated the activities of the radionuclides of interest.

The efficiency calibration was conducted by acquiring a calibration standard spectrum until the total absorption peak count rate was determined with a statistical uncertainty of less than 1% at a 95% confidence level. For the calculation of photo peaks, the net count rate was established to evaluate the output for all the energies used during the measurement. The output was then correlated with the count rate and the standard source using Equation 1<sup>21</sup>:

$$E_{\gamma} = \frac{N_{\epsilon}}{S_c \times \gamma_{\epsilon} \times t_c} \quad \text{Equation 1}$$

where  $N_{\epsilon}$  is the full energy peak net count,  $E_{\gamma}$  is the energy probability of gamma photons,  $\gamma_{\epsilon}$  is the probability of gamma emission,  $S_c$  is the activity of the standard source, while the counting time is  $t_c$ .

Gamma rays emitted from the standard reference source were measured, and the resulting spectrum was used to create the efficiency curve. Subsequently, power fitting was applied to optimise the  $R^2$ -value, as depicted in Figure 1.

The samples being counted had the same geometry as the standard references. The gamma transition energies of 1764.5, 2614 and 1640.8 keV were used to estimate the sample's radioactivity levels for  $^{226}\text{Ra}$ ,  $^{232}\text{Th}$  and  $^{40}\text{K}$ . Each sample was counted for 36 000 s (10 h). The counting time of 10 h (36 000 s) is selected to achieve high statistical accuracy by accumulating a large number of photon counts. This extended duration helps minimise statistical uncertainties in the measured gamma spectra, ensuring precise determination of radionuclide concentrations in the cement samples.<sup>22</sup>

Equation 2 was used to calculate the radioactivity concentration of the radionuclide from a measurement of the detector's efficiency<sup>23-25</sup>:

$$C_{sp} = \frac{N_{sam}}{P_{\epsilon} \cdot \epsilon \cdot T_c \cdot M} \quad \text{Equation 2}$$

where  $\epsilon$  is the detection system's overall counting efficiency,  $C_{sp}$  is the activity concentration of the radionuclides of interest in Bq/kg,  $N_{sam}$  is the radionuclide's net count in the sample,  $P_{\epsilon}$  is the probability of gamma ray emission (gamma yield),  $M$  is the sample's mass (in kg) and  $T_c$  is the sample counting time. The Data Analytical tool in Microsoft Excel 2010 running on Windows 10 was used for statistical analysis. To determine the minimum detection limit (MDL) for radionuclides  $^{226}\text{Ra}$ ,  $^{232}\text{Th}$  and  $^{40}\text{K}$  using gamma spectrometry, the background counts and the system's detection efficiency were evaluated. This calculation yields the smallest detectable radioactivity level above the background noise. The gamma spectrometric system's MDLs for  $^{226}\text{Ra}$ ,  $^{232}\text{Th}$  and  $^{40}\text{K}$  were 0.69, 0.78 and 2.35 Bq/kg, respectively. The MDL values provided signify the system's sensitivity to detect these radionuclides at extremely low levels, reflecting its capability under defined measurement conditions.

### Radiological health hazard indices assessment

In cement samples from the study area, activity concentrations of  $^{226}\text{Ra}$ ,  $^{232}\text{Th}$  and  $^{40}\text{K}$  have been studied for potential radiological risks that could impact human health due to radiation exposure. The radiological health impact metrics examined are the absorbed gamma dose rate, annual effective dose equivalent, annual gonadal dose equivalent (AGDE), excess lifetime cancer risk (ELCR), gamma index and alpha index.

### Absorbed gamma dose rate

The following equations were applied to the measured activity concentrations to calculate the indoor and outdoor absorbed gamma dose rates ( $D_{in}$  and  $D_{out}$ ) produced by gamma radiation caused by  $^{226}\text{Ra}$ ,  $^{232}\text{Th}$  and  $^{40}\text{K}$  at a height of 1 m above the ground<sup>26</sup>:

$$D_{in} (\text{nGy h}^{-1}) = 0.92 C_{Ra-226} + 1.1 C_{Th-232} + 0.081 C_{K-40} \quad \text{Equation 2a}$$

$$D_{out} (\text{nGy h}^{-1}) = 0.462 C_{Ra-226} + 0.0604 C_{Th-232} + 0.0417 C_{K-40} \quad \text{Equation 2b}$$

where the conversion factors for the doses associated with the radioactive concentrations of  $^{226}\text{Ra}$ ,  $^{232}\text{Th}$  and  $^{40}\text{K}$  for materials used as

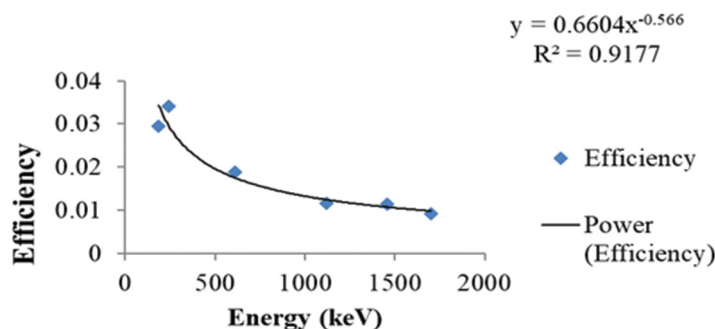


Figure 1: Efficiency calibration curve showing the detection efficiency of the detector.

building materials are 0.92, 1.1, 0.081, 0.462, 0.0604 and 0.0417 in nGyh<sup>-1</sup>/Bq/kg for indoor and outdoor, respectively.

### Annual effective dose

The annual effective dose (E) has been calculated using Equation 3a–3c<sup>26,27</sup>:

$$E_{in}(\mu\text{Svy}^{-1}) = 4.91 \times D_{in}(\text{nGyh}^{-1}) \quad \text{Equation 3a}$$

$$E_{out}(\mu\text{Svy}^{-1}) = 1.23 \times D_{out}(\text{nGyh}^{-1}) \quad \text{Equation 3b}$$

$$E_{tot}(\mu\text{Svy}^{-1}) = E_{in} + E_{out} \quad \text{Equation 3c}$$

The annual effective doses for indoor, outdoor and total exposure are  $E_{in}$ ,  $E_{out}$  and  $E_{tot}$ , respectively. The annual effective dose (E) was estimated using the following factors: the number of hours in a year (8610), the percentage of time spent indoors and outdoors (0.8 and 0.2) and the dose conversion factor of 0.7 Sv.Gy<sup>-1</sup>,<sup>26</sup> from the air-absorbed dose rate to an effective dose.

### Annual gonadal dose equivalent

The exceptionally high radiosensitivity of the human gonads, bone marrow and bone surface cells makes them organs of interest.<sup>28</sup> To calculate the AGDE, Equation 4 was utilised<sup>28</sup>:

$$\text{AGDE}(\mu\text{Svy}^{-1}) = 3.09C_{\text{Ra-226}} + 4.18C_{\text{Th-232}} + 0.0314C_{\text{K-40}} \quad \text{Equation 4}$$

where  $C_{\text{Ra-226}}$ ,  $C_{\text{Th-232}}$  and  $C_{\text{K-40}}$  are <sup>226</sup>Ra, <sup>232</sup>Th and <sup>40</sup>K activity concentrations in Bq/kg, respectively. Values 3.09, 4.18 and 0.0314 are the conversion factors for the doses associated with the radioactive concentrations of <sup>226</sup>Ra, <sup>232</sup>Th and <sup>40</sup>K in materials used as building materials, respectively.

### Gamma index and alpha index

To determine if the cement had complied with the radiological safety criteria for construction materials, the gamma index ( $I_\gamma$ ) was calculated using the following equation<sup>29</sup>:

$$I_\gamma = C_{\text{Ra}}/300 + C_{\text{Th}}/200 + C_{\text{K}}/3000 \quad \text{Equation 5a}$$

The alpha index ( $I_\alpha$ ), which symbolises the surplus alpha radiation brought on by breathing in radon-222 from the cement, was calculated using Equation 5b.

$$I_\alpha = C_{\text{Ra}}/200 \quad \text{Equation 5b}$$

**Table 1:** The reported <sup>226</sup>Ra, <sup>232</sup>Th and <sup>40</sup>K levels in the cement samples

| Sample ID | <sup>226</sup> Ra (Bq/kg) | <sup>232</sup> Th (Bq/kg) | <sup>40</sup> K (Bq/kg) |
|-----------|---------------------------|---------------------------|-------------------------|
| NPC 1     | 22.00 ± 2.51              | 20.00 ± 3.59              | 1662.00 ± 1.15          |
| NPC 2     | 15.00 ± 2.64              | 32.00 ± 0.51              | 569.00 ± 0.72           |
| NPC 3     | 8.00 ± 2.83               | 12.00 ± 0.90              | 1765.00 ± 0.93          |
| Mean      | 15.00 ± 2.66              | 21.33 ± 1.66              | 1332.00 ± 0.94          |
| Alpine 1  | 54.00 ± 4.80              | 29.00 ± 0.42              | 454.00 ± 0.56           |
| Alpine 2  | 16.00 ± 4.70              | 25.00 ± 0.24              | 1285.00 ± 1.73          |
| Alpine 3  | 35.00 ± 2.41              | 17.00 ± 0.48              | 1195.00 ± 1.33          |
| Mean      | 35.00 ± 3.97              | 23.67 ± 0.38              | 978.00 ± 1.21           |
| Dangote   | 45.00 ± 2.79              | 15.00 ± 1.28              | 1249.00 ± 0.63          |

where  $C_{\text{Ra-226}}$ ,  $C_{\text{Th-232}}$  and  $C_{\text{K-40}}$  are <sup>226</sup>Ra, <sup>232</sup>Th and <sup>40</sup>K activity concentrations in Bq/kg, respectively. 300, 200 and 3000 are the dose conversion factors associated with the radioactive concentrations of <sup>226</sup>Ra, <sup>232</sup>Th and <sup>40</sup>K for materials used as building materials for gamma index, while 200 is the dose conversion factor associated with the radioactive concentrations of <sup>226</sup>Ra in building materials for alpha index.

### Excess lifetime cancer risk

The annual effective dose (E) values computed as specified in Equation 6a–6c were used to calculate the ELCRs<sup>26,30</sup>:

$$\text{ELCR}_{in} = E_{in} \times D_i \times R_f \quad \text{Equation 6a}$$

$$\text{ELCR}_{out} = E_{out} \times D_i \times R_f \quad \text{Equation 6b}$$

$$\text{ELCR}_{tot} = \text{ELCR}_{in} + \text{ELCR}_{out} \quad \text{Equation 6c}$$

$R_f$  and  $D_i$  are the fatal cancer risk factors for stochastic effect (estimated 0.05 Sv<sup>-1</sup> for the general public) and lifetime duration (65.10 years for South Africa), respectively.

## Results and discussion

### Natural radioactivity concentrations


As shown in Table 1, the measured activity concentrations of <sup>226</sup>Ra, <sup>232</sup>Th and <sup>40</sup>K in cement samples are unevenly distributed.

The average activity concentration of <sup>226</sup>Ra in the cement samples was 27.857 Bq/kg, ranging from 8.00 ± 2.83 to 45.00 ± 2.79 Bq/kg. Dangote Cement (Sephaku) had the highest value of <sup>226</sup>Ra, while NPC 3 had the lowest value. With an average value of 21.43 Bq/kg, the measured activity concentrations of <sup>232</sup>Th in the cement samples ranged from 12.00 ± 0.90 to 32.00 ± 0.51 Bq/kg. NPC 2 and NPC 3 contained the highest and lowest results for <sup>232</sup>Th, respectively. With an average value of 1168.43 Bq/kg, the recorded activity concentrations of <sup>40</sup>K in the cement samples ranged from 454.00 ± 0.56 to 1765.00 ± 0.93 Bq/kg. Pretoria Portland cement (Alpine 1) had the lowest value, whereas NPC 3 had the highest value for <sup>40</sup>K, respectively. The world average values of radionuclides (<sup>226</sup>Ra, <sup>232</sup>Th and <sup>40</sup>K) in building materials are 50, 50 and 500 Bq/kg, respectively.<sup>28</sup> Alpine 1 had <sup>226</sup>Ra activity concentration value of 54.00 ± 4.80 Bq/kg, which is slightly higher than the world average value. The measured values and averages of the activity concentrations for <sup>226</sup>Ra and <sup>232</sup>Th in virtually all of the examined cement samples were found to be lower than the world average values. The average activity concentrations of <sup>40</sup>K in all the examined cement samples were found to be higher than the world average values, except for Alpine 1, which had an activity concentration value of 454.00 ± 0.56 Bq/kg, slightly lower than the world average. In general, the mean activity concentrations of <sup>40</sup>K were the highest in all the cement samples compared to the other two naturally occurring radionuclides (<sup>226</sup>Ra and <sup>232</sup>Th), respectively. This is typical and expected from any geologically derived materials because potash feldspar minerals are relatively enriched in the natural environment.<sup>31</sup> The concentrations of <sup>226</sup>Ra, <sup>232</sup>Th and <sup>40</sup>K in cement samples from the study locations are depicted in Figure 2.

The results of earlier research from various parts of the world were also compared with the calculated average values of the activity concentrations of naturally occurring radionuclides in the studied cement samples. Table 2 displays the comparison.

### Radiological hazard indices

Table 3 displays the findings of the assessed radiological health hazard parameters. The table shows that the assessed indoor and outdoor absorbed gamma dose rates ( $D_{in}$  and  $D_{out}$ ) varied from 95.089 to 176.862 nGyh<sup>-1</sup> and 49.985 to 91.549 nGyh<sup>-1</sup>. All of the cement samples' indoor absorbed gamma dose rates were above the population-weighted average of 84 nGyh<sup>-1</sup>.<sup>26</sup> The annual effective dose for indoor, outdoor

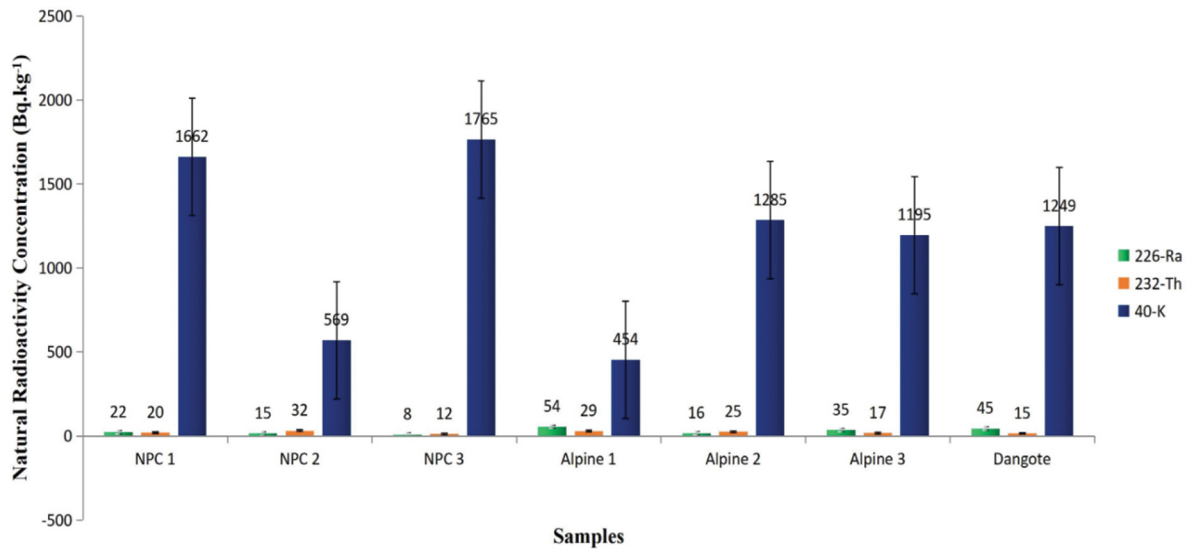

**Figure 2:** Activity concentration of <sup>226</sup>Ra, <sup>232</sup>Th and <sup>40</sup>K activity in the cement samples under study.

**Table 2:** Comparing the average concentrations of radionuclides (<sup>226</sup>Ra, <sup>232</sup>Th and <sup>40</sup>K) in cement samples to those discovered in other countries

| Sample ID          | Country       | <sup>226</sup> Ra (Bq/kg) | <sup>232</sup> Th (Bq/kg) | <sup>40</sup> K (Bq/kg) | Reference     |
|--------------------|---------------|---------------------------|---------------------------|-------------------------|---------------|
| NPC                | South Africa  | 15.00 ± 2.66              | 21.33 ± 1.66              | 1332.00 ± 0.94          | Present study |
| Alpine             | South Africa  | 35.00 ± 3.97              | 23.67 ± 0.38              | 978.00 ± 1.21           | Present study |
| Dangote            | South Africa  | 45.00 ± 2.79              | 15.00 ± 1.28              | 1249.00 ± 0.63          | Present study |
| Cement sample      | Albania       | 179.70 ± 8.90             | 55.00 ± 5.80              | 17.00 ± 3.30            | 32            |
| Cement sample      | Algeria       | 41.00 ± 7.00              | 27.00 ± 3.00              | 422.00 ± 3.00           | 33            |
| Cement sample      | Bangladesh    | 61.00                     | 65.00                     | 952.00                  | 34            |
| Cement sample      | Cameroon      | 27.00 ± 4.00              | 15.00 ± 1.00              | 277.00 ± 117.00         | 35            |
| Cement sample      | China         | 118.70 ± 14.20            | 36.10 ± 17.80             | 444.50 ± 163.10         | 36            |
| Cement sample      | China         | 59.00                     | 39.00                     | 181.00                  | 37            |
| Cement sample      | Egypt         | 36.00 ± 4.00              | 43.00 ± 2.00              | 82.00 ± 4.00            | 38            |
| Cement sample      | Egypt         | 134.00                    | 88.00                     | 416.00                  | 39            |
| Cement sample      | Ghana         | 35.94 ± 0.78              | 25.44 ± 0.80              | 233.00 ± 3.95           | 40            |
| Cement sample      | India         | 26.00                     | 29.00                     | 260.00                  | 41            |
| Cement sample      | Iraq          | 24.25 ± 1.45              | 25.41 ± 1.65              | 93.17 ± 7.30            | 42            |
| Cement sample      | Laos          | 41.12 ± 2.44              | 16.60 ± 2.37              | 141.48 ± 4.50           | 43            |
| Cement sample      | Malaysia      | 29.00 ± 7.00              | 31.00 ± 9.00              | 205.00 ± 71.00          | 44            |
| Cement sample      | Morocco       | 31.00 ± 5.00              | 19.00 ± 3.00              | 238.00 ± 13.00          | 45            |
| Cement sample      | Nigeria       | 20.00                     | 8.00                      | 51                      | 46            |
| Cement sample      | Pakistan      | 25.00 ± 10.00             | 37.00 ± 9.00              | 245.00 ± 95.00          | 47            |
| Cement sample      | Serbia        | 37.00                     | 15.00                     | 43.00                   | 48            |
| Cement sample      | Senegal       | 112.69 ± 26.02            | 13.12 ± 1.88              | 73.35 ± 18.12           | 49            |
| Cement sample      | Turkey        | 34.00 ± 4.00              | 15.00 ± 2.00              | 220.00 ± 13.00          | 50            |
| Cement sample      | Turkey        | 26.00                     | 10.00                     | 130.00                  | 51            |
| Building materials | World average | 50                        | 50                        | 500                     | 28            |

**Table 3:** Calculated radiological health hazard indices

| Sample ID | D <sub>in</sub><br>(nGyh <sup>-1</sup> ) | D <sub>out</sub><br>(nGyh <sup>-1</sup> ) | E <sub>in</sub><br>(μSvy <sup>-1</sup> ) | E <sub>out</sub><br>(μSvy <sup>-1</sup> ) | E <sub>tot</sub><br>(μSvy <sup>-1</sup> ) | AGDE<br>(μSvy <sup>-1</sup> ) | I <sub>γ</sub> | I <sub>α</sub> | ELCR <sub>in</sub> ×<br>10 <sup>-3</sup> | ELCR <sub>out</sub> ×<br>10 <sup>-3</sup> | ELCR <sub>tot</sub> ×<br>10 <sup>-3</sup> |
|-----------|--|---|--|---|---|-------------------------------|----------------|----------------|--|---|---|
| NPC 1     | 176.862                                  | 91.549                                    | 868.392                                  | 112.606                                   | 980.998                                   | 203.767                       | 0.727          | 0.110          | 2.827                                    | 0.367                                     | 3.193                                     |
| NPC 2     | 95.089                                   | 49.985                                    | 466.887                                  | 61.482                                    | 528.369                                   | 197.977                       | 0.400          | 0.075          | 1.520                                    | 0.200                                     | 1.720                                     |
| NPC 3     | 163.525                                  | 84.545                                    | 802.908                                  | 103.990                                   | 906.898                                   | 130.301                       | 0.675          | 0.040          | 2.613                                    | 0.338                                     | 2.952                                     |
| Mean      | 145.159                                  | 75.360                                    | 712.729                                  | 92.692                                    | 805.422                                   | 177.348                       | 0.601          | 0.075          | 2.320                                    | 0.302                                     | 2.622                                     |
| Alpine 1  | 118.354                                  | 61.396                                    | 581.118                                  | 75.517                                    | 656.635                                   | 302.336                       | 0.476          | 0.270          | 1.892                                    | 0.246                                     | 2.137                                     |
| Alpine 2  | 146.305                                  | 76.077                                    | 718.358                                  | 93.574                                    | 811.932                                   | 194.289                       | 0.607          | 0.080          | 2.338                                    | 0.305                                     | 2.643                                     |
| Alpine 3  | 147.695                                  | 76.270                                    | 725.183                                  | 93.811                                    | 818.994                                   | 216.733                       | 0.600          | 0.175          | 2.360                                    | 0.305                                     | 2.666                                     |
| Mean      | 137.451                                  | 71.247                                    | 674.886                                  | 87.634                                    | 762.520                                   | 237.786                       | 0.561          | 0.175          | 2.197                                    | 0.285                                     | 2.482                                     |
| Dangote   | 159.069                                  | 81.933                                    | 781.029                                  | 100.778                                   | 881.807                                   | 240.969                       | 0.641          | 0.225          | 2.542                                    | 0.328                                     | 2.870                                     |

and total exposure ranged from 466.887 to 868.392 μSvy<sup>-1</sup>, 61.482 to 112.606 μSvy<sup>-1</sup> and 528.369 to 980.998 μSvy<sup>-1</sup>, respectively. In NPC 1 and NPC 2, the highest and lowest values of the indoor and outdoor absorbed gamma dose rate and the indoor, outdoor and total annual effective dose were recorded. All of the samples' annual effective dose values were below the reference level of 1000 μSvy<sup>-1</sup>.<sup>26</sup> The AGDE ranged from 130.301 to 302.336 μSvy<sup>-1</sup>. While NPC 3 had the lowest value, PPC (Alpine 1) had the highest value of AGDE. Except for Alpine 1, whose yearly gonadal dose equivalent value was slightly higher at 302.336 μSvy<sup>-1</sup>. All of the samples' recorded values were below the 300 μSvy<sup>-1</sup> world average. The alpha index (I<sub>α</sub>) ranged from 0.040 to 0.270, and the gamma index (I<sub>γ</sub>) ranged from 0.040 to 0.727.

The gamma (I<sub>γ</sub>) and alpha (I<sub>α</sub>) index values fell below the recommended upper limit of unity.<sup>52</sup> For indoor (ELCR<sub>in</sub>), outdoor (ELCR<sub>out</sub>) and total (ELCR<sub>tot</sub>) ELCR, respectively, the ELCR values ranged from 1.520 × 10<sup>-3</sup> to 2.827 × 10<sup>-3</sup>, 0.200 × 10<sup>-3</sup> to 0.367 × 10<sup>-3</sup> and 1.720 × 10<sup>-3</sup> to 3.193 × 10<sup>-3</sup>. The ELCR<sub>in</sub> and ELCR<sub>tot</sub> reported in this study are higher than the world average values of 0.29 × 10<sup>-3</sup> and 1.45 × 10<sup>-3</sup> reported by Mohammed and Ahmed.<sup>53</sup> The values of ELCR equivalent to 1000, 100, 10 and 1 μSvy<sup>-1</sup> will increase the chance of developing fatal cancer by 4%, 0.4%, 0.04% and 0.004%, respectively.<sup>44,54</sup> The values of the risk obtained for this study are within the acceptable risk limits.

## Conclusion

According to the study, there were uneven distributions of the measured natural radioactivity concentrations of <sup>226</sup>Ra, <sup>232</sup>Th and <sup>40</sup>K in the cement samples. In almost all of the analysed cement samples, the measured values and averages of the activity concentrations for <sup>226</sup>Ra and <sup>232</sup>Th were lower than the global average. In contrast, in almost all of the analysed cement samples, the observed values and average activity concentrations for <sup>40</sup>K were higher than the global average levels provided by the UNSCEAR 2000 Report. The findings show that <sup>40</sup>K is the radionuclide in the environment with the highest measured radioactivity content. Radiological health impact measures, including absorbed gamma dose rate, annual effective dose, AGDE, ELCR, gamma index, and alpha index, were established to evaluate the potential radiation risks. The cement samples' indoor absorbed gamma radiation rates were higher than the population-weighted global average of 84 nGyh<sup>-1</sup> provided by the UNSCEAR in 2000. The annual effective dose and annual gonadal dose equivalent values for all the samples were lower than the reference level of 1000 μSvy<sup>-1</sup> and the world average value of 300 μSvy<sup>-1</sup>, respectively. The gamma index (I<sub>γ</sub>) and alpha index (I<sub>α</sub>) values were all below the reference level of unity. Even if all of the determined ELCRs are higher than the global average value, there is very little chance that this will increase cancer risk in the long run. However, <sup>40</sup>K naturally occurring radioactivity content was higher than the global average, which could serve as a warning to the radiation safety authority.

## Data availability

The data supporting the results of this study are available upon request to the corresponding author.

## Declarations

This study was carried out as part of O.Y.O.'s PhD research under the supervision of N.C. and co-supervision of A.O.I. at the University of KwaZulu-Natal, South Africa. We have no competing interests to declare. We have no AI or LLM use to declare.

## Authors' contributions

O.Y.O.: Collected the samples and prepared them for gamma ray spectrometry. N.C.: Conceived the study and supervised and guided the process of the research. A.O.I.: Co-supervised the research and participated in the spectrometric analysis. All authors read and approved the final manuscript.

## References

1. Imani M, Adelikhah M, Shahrokhi A, Azimpour G, Yadollahi A, Kocsis E, et al. Natural radioactivity and radiological risks of common building materials used in Semnan Province dwellings, Iran. *Environ Sci Pollut Res*. 2021;28:41492–41503. <https://doi.org/10.1007/s11356-021-13469-6>
2. Gupta M, Chauhan RP. Estimation of low-level radiation dose from some building materials using gamma spectroscopy. *Indoor Built Environ*. 2011; 21(3):465–473. <https://doi.org/10.1177/1420326x11414283>
3. Joshua EO, Ademola JA, Akpanowo MA, Oyebanjo O, Olorode DO. Natural radionuclides and hazards of rock samples collected from Southeastern Nigeria. *Radiat Meas*. 2009;44(4):401–404. <https://doi.org/10.1016/j.radmeas.2009.04.002>
4. Lust M, Realo E. Assessment of natural radiation exposure from building materials in Estonia. *Proc Est Acad Sci*. 2012;61(2):107–112. <https://doi.org/10.3176/proc.2012.2.03>
5. Maxwell O, Adewoyin O, Joel ES, Ehi-Eromosele CO, Akinwumi SA, Usikalu MR, et al. Radiation exposure to dwellers due to naturally occurring radionuclides found in selected commercial building materials sold in Nigeria. *J Radiat Res Appl Sci*. 2018;11(3):225–231. <https://doi.org/10.1016/j.jrras.2018.01.007>
6. Shoeib M, Thabayneh KM. Assessment of natural radiation exposure and radon exhalation rate in various samples of Egyptian building materials. *J Radiat Res Appl Sci*. 2014;7(2):174–181. <https://doi.org/10.1016/j.jrras.2014.01.004>
7. Donya M, Radford M, ElGuindy A, Firmin D, Yacoub MH. Radiation in medicine: Origins, risks and aspirations. *Glob Cardiol Sci Pract*. 2014;4:57. <https://doi.org/10.5339/gcsp.2014.57>

8. Chad-Umoren YE, Nwali AC. Assessment of specific activity concentration and percentage contribution of  $^{226}\text{Ra}$ ,  $^{232}\text{Th}$ , and  $^{40}\text{K}$  to the absorbed dose rate of the Port Harcourt Refinery Company host community. *Scientia Africana*. 2013;12(1):1–19. <https://www.ajol.info/index.php/sa/article/view/156889>
9. Desouky OS, Ding N, Zhou G. Targeted and non-targeted effects of ionizing radiation. *J Radiat Res Appl Sci*. 2015;8(2):247–254. <https://doi.org/10.1016/j.jrras.2015.03.003>
10. Ilori AO, Adeleye B. Radiation absorbed dose rates from selected mobile phone base stations in Ibadan, Oyo state, Nigeria. *J Sci Res Rep*. 2019;22(5):1–10. <https://doi.org/10.9734/jsrr/2019/v22i530100>
11. Kok P, Collinson M. Migration and urbanization in South Africa. Report 03-04-02. Pretoria: Statistics South Africa; 2006. <https://ci.nii.ac.jp/ncid/BA81432173>
12. Bakera AT, Alexander ME. Use of metakaolin as a supplementary cementitious material in concrete, with a focus on durability properties. *RILEM Tech Lett*. 2019;4:89–102. <https://doi.org/10.21809/rilemtechlett.2019.94>
13. Adetooto J, Windapo A, Pomponi F. The use of alternative building technologies as a sustainable affordable housing solution: Perspectives from South Africa. *J Eng Des Technol*. 2022;22(5):1447–1463. <https://doi.org/10.1108/jedt-05-2022-0257>
14. Aitcin P. Cement of yesterday and today. *Cem Concr Res*. 2000;30(9):1349–1359. [https://doi.org/10.1016/S0008-8846\(00\)00365-3](https://doi.org/10.1016/S0008-8846(00)00365-3)
15. Eldredge N, Horenstein S. Concrete jungle. Berkeley, CA: University of California Press eBooks; 2019. <https://doi.org/10.1525/9780520958302>
16. Maxwell O, Emmanuel JS, Olusegun AO, Cyril EO, Ifeanyi AJ, Embong Z. A study of natural radioactivity in some building materials in Nigeria. *Radiat Prot Dosim*. 2018;183(3):332–335. <https://doi.org/10.1093/rpd/ncy121>
17. Imani M, Adelikhah M, Shahrokhi A, Azimpour G, Yadollahi A, Kocsis E, et al. Natural radioactivity and radiological risks of common building materials used in Semnan Province dwellings, Iran. *Environ Sci Pollut Res*. 2021;28(30):41492–41503. <https://doi.org/10.1007/s11356-021-13469-6>
18. Lewicka S, Piotrowska B, Łukaszek-Chmielewska A, Drzymala T. Assessment of natural radioactivity in cements used as building materials in Poland. *Int J Environ Res Public Health*. 2022;19(18):11695. <https://doi.org/10.3390/ijerph191811695>
19. IAEA. Radiation protection and safety of radiation sources: International basic safety standards. In: International Atomic Energy Agency eBooks; 2014. <http://s://doi.org/10.61092/iaea.u2pu-60vm>
20. ICRP. The 2007 Recommendations of the International Commission on Radiological Protection. ICRP Publication 103. *Ann ICRP*. 2007;37(2-4).
21. ICRP. 1990 recommendations of the International Commission on Radiological Protection, ICRP Publication 60. *Ann ICRP*. 1991;21(1-3):1–201.
22. Bavarnegin E, Moghaddam MA, Fathabadi N. Natural radionuclide and radiological assessment of building materials in high background radiation areas of Ramsar, Iran. *J Med Phys*. 2013;38(2):93–97. <https://doi.org/10.4103/0971-6203.111325>
23. Alaamer AS. Assessment of human exposure to natural radiation sources in the soil of Riyadh, Saudi Arabia. *Turk J Eng Environ Sci*. 2008;32:229–234.
24. Dhawal SJ, Kulkarni GS, Pawar SH. Terrestrial background radiation studies in South Konkan, Maharashtra, India. *Int J Radiat Res*. 2013;11:263–270. <http://ijrr.com/article-1-1106-en.html>
25. Ilori AO, Chetty N, Adeleye B. Assessment of radiological hazard indices due to natural radionuclides in the soil of Irele local government area, Ondo state Nigeria. *Environ Forensics*. 2023;25(4):173–179. <https://doi.org/10.1080/15275922.2023.2172096>
26. United Nations Scientific Committee on the Effects of Atomic Radiation. Sources and effects of ionizing radiation: 2000 report to the general assembly, with scientific annexes. New York: United Nations; 2000 [cited 2023 Jul 14]. Available from: [https://www.unscear.org/unscear/en/publications/2000\\_1.html](https://www.unscear.org/unscear/en/publications/2000_1.html)
27. Ibitola GA, Ajanaku O, Ilori AO, Aremu RO, Omosebi IAA. Measurement of  $^{40}\text{K}$ ,  $^{238}\text{U}$ , and  $^{232}\text{Th}$  and associated dose rates in soil and commonly consumed foods (vegetables and tubers) at Okitipupa, Ondo state, southwestern Nigeria. *Asian J Res Rev Phys*. 2018;1(1):1–11. <https://doi.org/10.9734/ajr2p/2018/v1i124597>
28. United Nations Scientific Committee on the Effects of Atomic Radiation. Sources and effects of ionizing radiation: 1993 report to the general assembly, with scientific annexes. New York: United Nations; 1993 [cited 2023 Jul 14]. <https://www.unscear.org/unscear/en/publications/1993.html>
29. Khan MF, Benjamin J, Wesley SG. Radiotoxicity via intake of marine organisms: Exposure and risk assessment in South Indians. *Toxicol Environ Chem*. 2011;93(3):549–564. <https://doi.org/10.1080/02772248.2010.548118>
30. Ilori AO, Chetty N. Activity concentrations and radiological hazard assessments of  $^{226}\text{Ra}$ ,  $^{232}\text{Th}$ , and  $^{40}\text{K}$  in soil samples of oil-producing areas of South Africa. *Int J Environ Health Res*. 2022;32(12):2665–2677. <https://doi.org/10.1080/09603123.2021.1984399>
31. IAEA. Analytical methodology for the determination of radium isotopes in environmental samples. IAEA analytical quality in Nuclear Applications Series No. 19, IAEA, Vienna; 2010 [cited 2023 Jul 19]. <https://www.iaea.org/publications/8536/analytical-methodology-for-the-determination-of-radium-isotopes-in-environmental-samples>
32. Xhixha G, Ahmeti A, Bezzon GP, Bitri M, Broggin C, Buso GP, et al. First characterisation of natural radioactivity in building materials manufactured in Albania. *Radiat Prot Dosim*. 2013;155(2):217–223. <https://doi.org/10.1093/rpd/ncs334>
33. Amrani D, Tahtat M. Natural radioactivity in Algerian building materials. *Appl Radiat Isot*. 2001;54(4):687–689. [https://doi.org/10.1016/S0969-8043\(00\)00304-3](https://doi.org/10.1016/S0969-8043(00)00304-3)
34. Asaduzzaman K, Mannan F, Khandaker MU, Farook MS, Elkezza A, Amin YBM, et al. Assessment of natural radioactivity levels and potential radiological risks of common building materials used in Bangladeshi dwellings. *PLoS ONE*. 2015;10(10), e0140667. <https://doi.org/10.1371/journal.pone.0140667>
35. Ngachin M, Garavaglia M, Giovani C, Njock MK, Nourredine A. Assessment of natural radioactivity and associated radiation hazards in some Cameroonian building materials. *Radiat Meas*. 2007;42(1):61–67. <https://doi.org/10.1016/j.radmeas.2006.07.007>
36. Li X, Chao S, Yang F. Determination of natural radioactivity and associated radiation hazard in building materials used in Weinan, China. *Radiat Phys Chem*. 2014;99:62–67. <https://doi.org/10.1016/j.radphyschem.2014.02.021>
37. Li X. Natural radioactivity in some building materials and by-products of Shaanxi, China. *J Radioanal Nucl Chem*. 2004;262(3):775–777. <https://doi.org/10.1007/s10967-004-0509-4>
38. El-Taher A. Gamma spectroscopic analysis and associated radiation hazards of building materials used in Egypt. *Radiat Prot Dosim*. 2009;138(2):166–173. <https://doi.org/10.1093/rpd/ncp205>
39. Ahmed NS. Measurement of natural radioactivity in building materials in Qena city, Upper Egypt. *J Environ Radioact*. 2005;83(1):91–99. <https://doi.org/10.1016/j.jenvrad.2005.03.002>
40. Kpeglo DO, Lawlusi H, Faanu A. Natural radioactivity and its associated radiological hazards in Ghanaian cement. *Res J Environ Earth Sci*. 2011;3(2):161–167. <https://maxwellsci.com/jp/abstract.php?jid=RJEES&no=89&abs=13>
41. Kerur BR, Rajeshwari T, Siddanna R, Kumar AS. Implication and hazard of radiation level in the building materials. *Acta Geophys*. 2013;61:1046–1056. <https://doi.org/10.2478/s11600-013-0109-1>
42. Mansoor ZA. Assessment of natural radioactivity levels and radiological hazards of cement in Iraq. *Nucl Sci*. 2018;3(2):23–27. <https://doi.org/10.11648/j.ns.20180302.11>
43. Xayheungsy S, Khiem LH, Nam LD. Assessment of the natural radioactivity and radiological hazards in Lao cement samples. *Radiat Prot Dosim*. 2018;181(3):208–213. <https://doi.org/10.1093/rpd/ncy014>
44. Abdullahi S, Ismail AF, Samat S. Determination of indoor doses and excess lifetime cancer risks caused by building materials containing natural radionuclides in Malaysia. *Nucl Eng Technol*. 2019;51(1):325–336. <https://doi.org/10.1016/j.net.2018.09.017>
45. Kassi B, Boukhar A, Azkour K, Fahad M, Benjelloun M, Nourredine A. Assessment of exposure due to technologically enhanced natural radioactivity in various samples of Moroccan building materials. *World J Nucl Sci Technol*. 2018;08(04):176–189. <https://doi.org/10.4236/wjnst.2018.84015>

46. Arabi AS, Funtua II, Dewu BBM, Muhammad A. Background radiation and radiological hazard associated with local building materials around Zaria, Nigeria. *Radiochemistry*. 2015;57(2):207–212. <https://doi.org/10.1134/s1066362215020149>
47. Faheem M, Mujahid SA, Matiullah. Assessment of radiological hazards due to the natural radioactivity in soil and building material samples collected from six districts of the Punjab province-Pakistan. *Radiat Meas*. 2008;43(8):1443–1447. <https://doi.org/10.1016/j.radmeas.2008.02.014>
48. Pantelić GK, Todorović D, Nikolić JD, Rajčić M, Janković M, Sarap N. Measurement of radioactivity in building materials in Serbia. *J Radioanal Nucl Chem*. 2014;303:2517–2522. <https://doi.org/10.1007/s10967-014-3745-2>
49. Ndour O, Thiandoume C, Traore A, Cagnat X, Diouf PM, Ndeye M, et al. Assessment of natural radioactivity and its radiological hazards in several types of cement used in Senegal. *SN Appl Sci*. 2020;2:2078. <https://doi.org/10.1007/s42452-020-03904-7>
50. Özdiş BE, Cam N, Öztürk BC. Assessment of natural radioactivity in cement used as building materials in Turkey. *J Radioanal Nucl Chem*. 2016;311(1):307–316. <https://doi.org/10.1007/s10967-016-5074-0>
51. Mavi B, Akkurt I. Natural radioactivity and radiation hazards in some building materials used in Isparta, Turkey. *Radiat Phys Chem*. 2010;79(9):933–937. <https://doi.org/10.1016/j.radphyschem.2010.03.019>
52. EC-European Commission. Radiological protection principles concerning the natural radioactivity of building materials. *Radiat Prot*. 1999;112:1–16.
53. Mohammed RS, Ahmed RS. Estimation of excess lifetime cancer risk and radiation hazard indices in southern Iraq. *Environ Earth Sci*. 2017;76:1–9. <https://doi.org/10.1007/s12665-017-6616-7>
54. Gad A, Saleh AH, Khalifa MM. Assessment of natural radionuclides and related occupational risk in agricultural soil, Southeastern Nile Delta, Egypt. *Arab J Geosci*. 2019;12:1–15. <https://doi.org/10.1007/s12517-019-4356-6>